

Spin dependent non-tunneling transport in granular ferromagnet

Soumik Mukhopadhyay and I. Das

Saha Institute of Nuclear Physics, 1/AF, Bidhannagar, Kolkata 700064, India

We have shown that, at low temperature, the effect of localization of charge carriers in granular metals cannot be ignored. The electron localization in granular ferromagnetic metals can give rise to non-linear transport in the moderate electric field regime, which is dominated by spin dependent inter-grain non-tunneling emission. In contrast to the general opinion that spin dependent tunneling gives rise to low field magnetoresistance in granular ferromagnetic metals we observe that spin dependent non-tunneling transport is primarily responsible for the sharp magnetic field dependence of resistance, at least in the low temperature and moderate electric field regime.

PACS numbers: 72.25.-b, 73.63.-b, 85.75.-d

Recent emergence of spin based electronics or spintronics has initiated extensive studies on spin polarized transport in magnetic tunnel junctions, granular ferromagnetic films and nanocomposites. The low field magnetoresistance in magnetic tunnel junctions (MTJ), and granular ferromagnetic systems is attributed to spin dependent tunneling [1, 2, 3]. However, it has been shown recently that the superposition of tunneling conduction and ballistic channels can lead to inversion of magnetoresistance [4] in MTJs. This letter explores the possibility of whether there exists any transport mechanism other than spin dependent tunneling which might affect low field magnetoresistance in granular ferromagnets. Although the study of granular ferromagnetic metals spans more than three decades [2], recently, there is a renewed interest in this field with the granular systems based on “half metallic” materials like CrO_2 and $\text{La}_{0.67}\text{Sr}_{0.33}\text{MnO}_3$ showing enhanced low field magnetoresistance [3] leading to the possibility of their application as magnetic field sensors. We will analyze the effect of electron localization in granular ferromagnetic systems at sufficiently low temperature. The consequent dominance of spin dependent inter-grain non-tunneling emission over inter-grain tunneling in the moderate electric field regime will be discussed.

For the preparation of granular film with almost uniform grain size distribution and quasi-homogeneous distribution of conducting and non-conducting regions, we have utilized the well studied strain relaxation properties of manganite films. Manganites like $\text{La}_{0.67}\text{Sr}_{0.33}\text{MnO}_3$ (LSMO) can be grown epitaxially on single crystal insulating substrate LaAlO_3 (LAO). However, due to finite lattice mismatch ($\{a_{\text{LSMO}} - a_{\text{LAO}}\}/a_{\text{LAO}} \sim +2\%$) with the substrate, thin films of $\text{La}_{0.67}\text{Sr}_{0.33}\text{MnO}_3$ undergoes a biaxial in plane compressive stress leading to higher out of plane lattice parameter compared to the substrate [5, 6, 7]. Relatively thick films (usually above 50 nm) become strain relaxed forming granular nanostructures and the grain size depends on the thickness of the film. In granular manganite systems, it is an established fact that the core of grain is ferro-magnetically ordered but the grain surface is spin-disordered and in-

sulating [8, 9].

Thick films of LSMO, having thickness $\sim 3000\text{\AA}$, were grown on $\text{LaAlO}_3(100)$, using pulsed laser deposition. The surface morphology of the film was inspected, using atomic force microscopy which shows orderly arrangement of connected grains with average size 80 nm (Fig: 1). In order to prove that this is not a mere surface corrugation, the x-ray diffraction $\theta - 2\theta$ scan around (002) peaks of LSMO/LAO are shown in Fig: 2A and the magnetic measurements in Fig: 3. The Bragg peak corresponding to that portion of the film which matches with the in-plane lattice parameters of the substrate leading to higher c-axis parameter is indicated in the figure as (1) which gradually relaxes to the bulk lattice parameter value shown by the higher angle peak among the twin peaks separated by a plateau indicated as (2). The intensity of Bragg peak which corresponds to strain relaxed part of the film is much higher compared to the strained part indicating that the granularity extends deep inside the film and hence bound to influence the transport and magnetic properties of the film. The magnetic characterization was done using a Quantum Design SQUID magnetometer which shows the ferromagnetic transition temperature T_c at around 360 K. The large irreversibility in the temperature dependence of zero field cooled (ZFC) and field cooled (FC) magnetization (M) together with the hysteric $M - H$ loop, where the magnetization does not saturate even at 2 kOe, are typical of granular ferromagnets (Fig: 3A,B). The virgin $M - H$ curve shows (Fig: 3) an ‘S’-like shape with the point of inflexion around 100 Oe indicating non-ferromagnetic inter-grain coupling. The coercivity of the film has roughly the same value.

The transport properties were studied using four probe technique with the magnetic field being in-plane to the electric field. The granular film exhibits a sharp rise in resistance (Fig: 4B) with lowering of temperature below around 6 K in the absence of external magnetic field. At higher bias current, the rise in resistance reduces drastically suggesting non-ohmic transport at low temperature. A significant reduction of percentage rise in resistance on application of magnetic field is observed. Hence Ziese’s

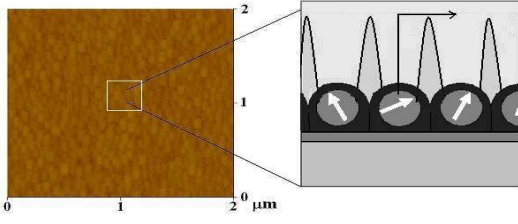


FIG. 1: AFM picture of the strain relaxed film over $2 \times 2 \mu\text{m}^2$ area showing the granular surface morphology along with a schematic cross-sectional blown-up view with strain-relaxed granular part and a thin strained bottom part, the grains (the ferromagnetically ordered core part) being assimilated to localized sites at low temperature, leading to the dominance of inter-grain non-tunneling transport.

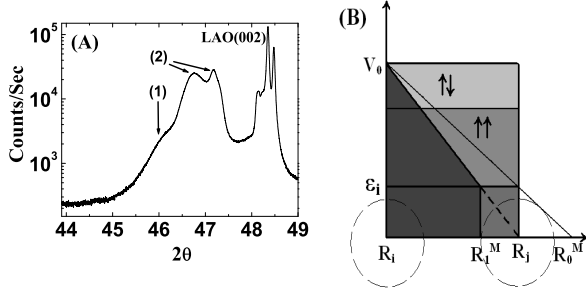


FIG. 2: **A:** X-ray diffraction pattern of the LSMO film on LAO substrate. The c-axis parameter of the film relaxes gradually to the bulk value of LSMO. The broad hump at the lower angle (1) indicates the strained part whereas the two broad peaks (2) and the plateau in between corresponds to the gradual relaxation of the strain. **B:** The conduction is due to the combined effect of tunneling through the barrier and thermal activation over the barrier. The effective barrier height depends on the relative spin orientation of adjacent sites. The conduction is in the moderate electric field regime where $R_j - R_1^M \ll R_j - R_i$

model of quantum interference effect [10] is not applicable here. Below 6 K, the strain relaxed film exhibits low field magnetoresistance which is extremely sensitive to the applied bias (Fig: 4C).

The electric field dependence of conductivity at 2 K, plotted in Fig: 4B, shows that the logarithm of conductivity is linearly proportional to square root of the electric field (E). At 5 K, very close to the point of upturn in resistance with lowering of temperature, the transport becomes nearly ohmic (Fig: 4D). Such electric field dependence is strikingly similar to the charge transport mechanism called Poole-Frenkel emission (PFE) [11]. The PFE, usually observed in disordered semiconducting systems, is a non-tunneling transport phenomenon where the charge carriers are thermally activated over the potential barrier from localized charge traps in the presence of electric field. The reduction in barrier height ϕ_{PF} is proportional to the square root of applied electric field and the conductivity is given by $G = G_0 \exp(\beta_{PF} E^{1/2}/KT)$,

where β_{PF} is a constant.

However, in this case what is fundamentally different from traditionally observed PFE is the tunability of the phenomenon by application of even a small amount of magnetic field. It is evident from Fig: 5A that the threshold electric field for the onset of charge emission E_{th} (indicated by the vertical arrow) and the slope of the curve are higher at 100 Oe magnetic field compared to that at 1 kOe. The origin of PF type emission in granular metal can be explained following Mostefa's model [12]. This model considers a granular metallic system with a narrow grain size distribution with almost equal Fermi levels for all grains and as a result the activation energy is entirely due to the potential barrier between two adjacent grains. In each grain, electrons can be considered as being localized at sufficiently low temperature. At low temperature, the leakage of electron wave function outside the grain is minimal, which is particularly true for insulating grain surfaces, as in this case [8, 9]. This justifies the assumption of grains as localized sites at sufficiently low temperature. In the weak field regime, the transport is purely thermally activated. The electric field will affect two important parameters of the system if it is above the weak field regime.

Firstly, the shape of the potential barriers and hence the decay of the wave function associated with the electronic states. The tunneling probability $P(R_{ij})$ between two grains assumed to be located at sites $\vec{R}_i$ and $\vec{R}_j$ separated by a distance $R_{ij} = |\vec{R}_j - \vec{R}_i|$ can be written, using WKB approximation,

$$P(R_{ij}) \simeq \exp \left[-\frac{2}{\hbar} \int_{\vec{R}_i}^{\vec{R}_j} \{2m[V(x) - \varepsilon_i]\}^{1/2} dx \right]$$

Here $V(x)$ is barrier height, x is the position of the electron on the path $\vec{R}_{ij}$ and ε_i is the electron energy in the grain located at i th site. It is assumed that the potential barrier is in the moderate field regime where the electron is emitted as a free particle into the insulator over a path much shorter than the total distance between the grains. The effective barrier height is $\phi_i(x) = V(x) - \varepsilon_i$. Taking these factors into consideration and assuming directed flow of electrons we get, $P(R_{ij}) \simeq \exp \left\{ -\frac{A}{E} \right\}$, where A is a constant.

Secondly, the activation energy E_a required for one electron to hop from a neutral grain to another neutral grain. In the non-negligible field regime, the activation energy required to transfer an electron from site i to site j is, $E_a^{ij} = \varepsilon_{ij} - e\vec{E} \cdot \vec{R}_{ij}$, where, $\varepsilon_{ij} = \varepsilon_i - \varepsilon_j$. Hence the activation probability,

$$P(E_a^{ij}) \simeq \exp \left\{ \frac{-\varepsilon_{ij}}{KT} + \frac{eER_{ij} \cos \theta}{KT} \right\}$$

The electrical conductance G_{ij} between sites i and j can be calculated from the total transport probability P_{ij} ,

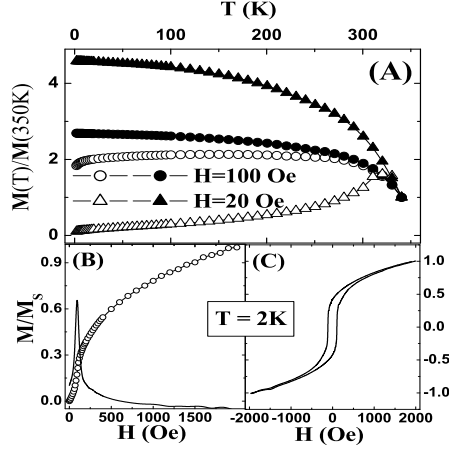


FIG. 3: **A:** The zero field cooled (ZFC) (open symbols) and field cooled (FC) (filled symbols) M vs. T curves at magnetic fields $H = 20$ Oe and $H = 100$ Oe showing irreversibility between the ZFC and FC curves which is an evidence for the granularity of the film. **B:** Virgin M vs. H curve for the strain relaxed film at 2 K, exhibiting inflexion at 100 Oe shown by the slope of the curve plotted as continuous line. **C:** M vs. H hysteresis loops at 2 K, showing coercivity of about 100 Oe.

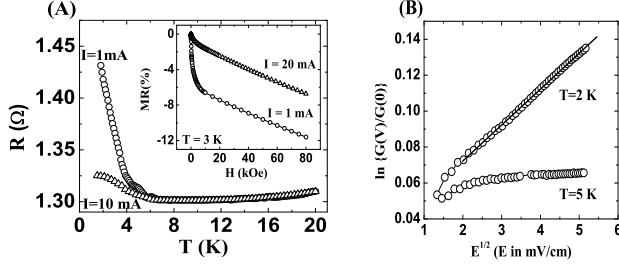


FIG. 4: **A:** Rise in resistance with lowering of temperature below 6 K at different bias currents, suggesting non-ohmic transport below 6 K. Inset: Magnetic field dependence of MR at 3 K at different bias currents. **B:** Plot of logarithm of dc conductivity vs. $E^{1/2}$ in absence of magnetic field at 2 K and 5 K for the same sample. The linear region in the curve (for 2 K) indicates thermally assisted non-tunneling emission due to localization of charge carriers at low temperature. The non-tunneling emission is almost suppressed at 5 K.

which is given by the product of the tunneling probability across the barrier and the activation probability over the barrier. Assuming that the temperature is low enough to help the hopping transport, the conductance can be calculated employing percolative treatment.

However, Mostefa's model alone cannot explain the sharp magnetic field dependence discussed earlier. Therefore, we incorporate an additional inter-grain magnetic exchange energy (E_m) term in the model. It arises due to the relative spin orientation of the two adjacent localized sites when the spin is conserved in hopping from

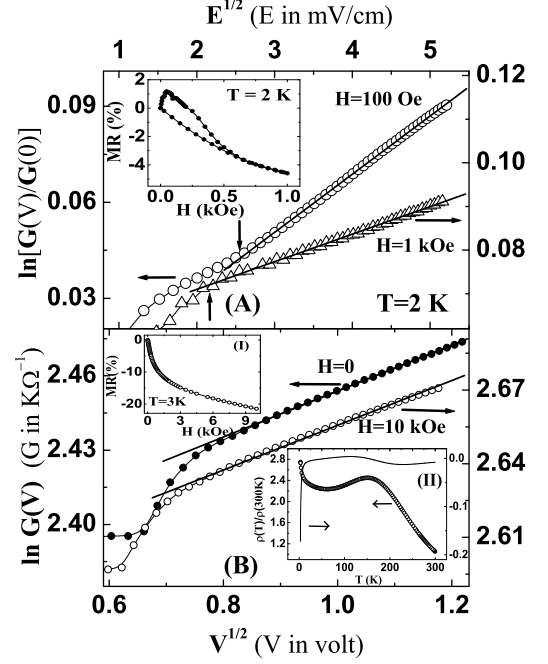


FIG. 5: Sensitivity of the PF type emission to magnetic field. Plot of logarithm of dc conductivity vs. $E^{1/2}$ in the antiparallel and parallel magnetic configuration with the corresponding magnetic field dependence of magnetoresistance at the same temperature in the inset for the strain relaxed film (A) and (LSMO) $_{1-x}$ (ALO) $_x$ composite with $x = 0.5$ (B). The threshold electric field E_{th} is indicated by the vertical arrow. The additional inset (II) in (B) describes the temperature dependence of resistance of the same sample with a rapid increase in slope below 10 K shown by the continuous line.

one site to another. The value of E_m depends on the overlap of electronic wave function across the grains. If the spin orientation is anti-parallel an additional energy $+E_m$ is necessary for charge carrier emission while less energy $-E_m$ is required if the orientation is parallel. Obviously, the value of E_m can easily be manipulated by applying even a tiny magnetic field H . Hence the prescription is to simply replace the effective potential barrier $\phi_i(x)$ by $\phi_i^m(x) = \phi_i(x) \pm E_m^{ij}(H)$ and the activation energy E_a^{ij} by $E_a^{ij,m} = \varepsilon_{ij} - e\vec{E} \cdot \vec{R}_{ij} \pm E_m^{ij}(H)$. Now we employ the percolation criterion $G_{ij} \geq G_C$, where G_C is the critical conductance for percolation. This sets a limit on the energy and the length scales ($\varepsilon_{ij} \leq \varepsilon_M$ and $R_{ij} \leq R_M$) involved and one arrives at, $\frac{\varepsilon_{ij}}{\varepsilon_M} - \frac{R_{ij}}{R_M} \leq 1$ [12] where, $\varepsilon_M = \left(\frac{KT}{1 \pm \xi_m}\right) Y'$, $S_M = \left(\frac{KT}{eE}\right) Y'$ and $Y' = \ln \frac{G'_C}{G_C}$. Here the magnetic exchange energy has been expressed in the unit of ε_{ij} as $E_m = \xi_m \varepsilon_{ij}$, where ξ_m is a dimensionless quantity. Then following Mostefa's derivation one

obtains,

$$\log\left(\frac{G_C}{G_0}\right) = B(H)\frac{E^{1/2}}{KT}$$

where $B_{\uparrow\downarrow,\uparrow\uparrow} \propto \sqrt{1 \pm \xi_m}$ for a given system, with $\uparrow\downarrow$ and $\uparrow\uparrow$ indicating the antiparallel and parallel magnetic configuration between nearest neighboring grains, respectively. Evidently, the value of B is higher in the antiparallel configuration compared to the parallel one.

It is interesting to compare the magnetoresistance (Inset, Fig: 5A) with the conductivity curves at different magnetic fields in Fig: 5A at low temperature. The magnetoresistance is positive at 100 Oe, which is equal to the coercivity and the inflexion point in the virgin $M - H$ curve (Fig: 3). This suggests that at this point, the spin orientation between the adjacent grains becomes anti-parallel, resulting in increase of exchange energy. The increase in the slope of the logarithmic conductivity vs. $E^{1/2}$ curve at $H = 100$ Oe in Fig: 5 compared to that at $H = 1$ kOe is consistent with our model. The value of exchange energy can be estimated from the slope of the curves at 100 Oe (antiparallel configuration) and 1 kOe (parallel configuration) using the relation $\xi_m = (B_{\uparrow\downarrow}^2 - B_{\uparrow\uparrow}^2)/(B_{\uparrow\downarrow}^2 + B_{\uparrow\uparrow}^2)$ which gives $\xi_m = 0.79$ and therefore $E_m = 0.79\varepsilon_{ij}$. The validity of the non-tunneling emission being limited to the moderate electric field regime (as defined in Fig: 2B) is determined partly by the potential barrier height. Therefore, the shift in the threshold electric field (E_{th}) for the onset of PF type emission should be magnetic field dependent since magnetic exchange energy contributes substantially to the total barrier height. In the antiparallel configuration, the value of E_{th} should be higher in comparison with the parallel configuration, which is consistent with our observation. A rough estimation of the average total activation energy (including the magnetic contribution) is possible from the fitting of temperature dependence of resistance (at low temperature and bias) in absence of magnetic field by an activation term with a metallic contribution in parallel. The metallic channel includes whatever the effect of the thin continuous strained part might have. Consequently, the magnetic exchange energy turns out to be $E_m \sim 0.24$ K. Similar value (~ 0.23 K) can be extracted from the difference in the total activation energy values in the absence and in presence of magnetic field, respectively.

In order to find out whether the same phenomenon is operative in a different micro-structure, we have studied magnetotransport properties in a nanocrystalline LSMO/ Al_2O_3 (ALO) granular composite with different weight concentrations x of Al_2O_3 (where $x = 0 - 0.5$). The average grain size of the sol-gel prepared LSMO was measured, using Transmission Electron Microscope (TEM) and Scanning electron microscope (SEM), which turns out to be about 50 nm. Fig: 5B shows similar spin dependent non-tunneling emission in LSMO/ALO

composite with $x = 0.5$ at 3 K. The temperature dependence of resistance shows a low temperature upturn with a rapid increase in the slope below 10 K (Inset II, Fig: 5B). All other samples with different values of x , exhibit similar behavior. This suggests that the effect of localization at low temperature and the consequent dominance of non-tunneling effect might be generic to a large variety of granular ferromagnetic metals. Employing the same method for estimation of magnetic exchange energy described in the previous paragraph we obtain $\xi_m = 0.04$ only. The temperature dependence of resistance can be fitted using the parallel channel conduction model of ref. [13], which gives a rough estimate of activation energy to be ~ 0.8 K. The reduction in the slope of the curve as well as E_{th} with applied magnetic field is not as pronounced as in the case of strain-relaxed film indicating that the value of exchange energy should be comparatively smaller. The small value of exchange energy in this case can be understood considering the larger average inter-particle separation in the composite. Thus the sensitivity of the slope of the logarithmic conductance vs. $E^{1/2}$ curves in the non-tunneling regime as well as that of E_{th} to the magnetic field depends on the relative contribution of the magnetic exchange to the total activation energy. This factor is determined by the microstructure of the granular system along with the spin polarization of the ferromagnetic grains.

To conclude, we have observed spin dependent non-tunneling transport in LSMO granular film and LSMO/ALO metal-insulator nanocomposites, a phenomenon which appears to be generic to ferromagnetic granular metallic systems, particularly at low temperature. In contrast to the usual Poole-Frenkel emission, the electric field dependence of conductivity is sensitive to external magnetic field. The observed phenomenon has been analyzed considering the dominance of thermally assisted inter-grain non-tunneling transport (with the grains acting as localized sites) in the moderate electric field regime and the existence of an additional inter-grain magnetic exchange barrier.

The authors acknowledge Prof. A. K. Raychaudhuri and Dr. Barnali Ghosh of SBNCBS, Kolkata for providing some experimental facilities.

-
- [1] J. S. Moodera, Lisa R. Kinder, Terrilyn M. Wong, R. Meservey, Phys. Rev. Lett., **74**, 3273 (1995)
 - [2] Helman J. S. and Abeles B., Phys. Rev. Lett., **37**, 1429 (1976)
 - [3] H. Y. Hwang, S-W. Cheong, N. P. Ong, and B. Batlogg Phys. Rev. Lett. **77**, 2041 (1996)
 - [4] Soumik Mukhopadhyay, I. Das, Phys. Rev. Lett, **96**, 026601 (2006)
 - [5] S. I. Khartsev, P. Johnson, and A. M. Grishin, J. Appl. Phys. **87**, 2394 (2000)

- [6] Mandar Paranjape, A. K. Raychaudhuri, N. D. Mathur, and M. G. Blamire, Phys. Rev. B **67**, 214415 (2003)
- [7] M. Ziese, H. C. Semelhack, K. H. Han, S. P. Sena, and H. J. Blythe, J. Appl. Phys. **91**, 9930 (2002)
- [8] L. Balcells, J. Fontcuberta, B. Martnez, and X. Obradors Phys. Rev. B **58**, R14697 (1998)
- [9] Barnali Ghosh, Sohini Kar, Loveleen K. Brar, A. K. Raychaudhuri, J. Appl. Phys. **98**, 094302 (2005)
- [10] M. Ziese, Phys. Rev. B, **68**, 132411 (2003)
- [11] Frenkel J., Phys. Rev., **54**, 647 (1938)
- [12] M. Mostefa, D. Bourbie and G. Olivier, Physica B, **160**, 186 (1989)
- [13] A. de Andres, M. Garcia-Hernandez, and J. L. Martinez, Phys. Rev. B **60**, 7328 (1999)